

## **General Disclaimer**

### **One or more of the Following Statements may affect this Document**


- This document has been reproduced from the best copy furnished by the organizational source. It is being released in the interest of making available as much information as possible.
- This document may contain data, which exceeds the sheet parameters. It was furnished in this condition by the organizational source and is the best copy available.
- This document may contain tone-on-tone or color graphs, charts and/or pictures, which have been reproduced in black and white.
- This document is paginated as submitted by the original source.
- Portions of this document are not fully legible due to the historical nature of some of the material. However, it is the best reproduction available from the original submission.

(NASA-CR-153698) TWO-DIMENSIONAL  
HYGROTHERMAL DIFFUSIONS INTO A FINITE WIDTH  
COMPOSITE LAMINATE Interim Report (Virginia  
Polytechnic Inst. and State Univ.) 30 p  
HC A03/MF A01 CSCL 11D G3/24 38269

N77-27189

Unclas  
38269

# COLLEGE OF ENGINEERING

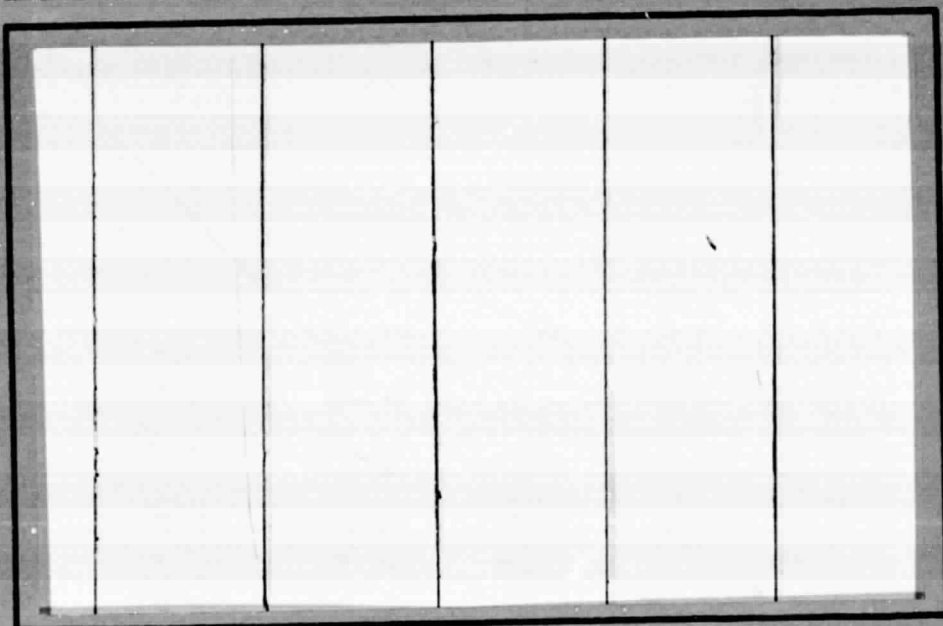

**VIRGINIA  
POLYTECHNIC  
INSTITUTE  
AND  
STATE  
UNIVERSITY**

**BLACKSBURG,  
VIRGINIA**

College of Engineering  
Virginia Polytechnic Institute and State University  
Blacksburg, VA. 24061

VPI-E-77-20

June, 1977

Two-Dimensional Hygrothermal Diffusions Into  
a Finite Width Composite Laminate

Gary L. Farley<sup>1</sup>

Carl T. Herakovich<sup>2</sup>

Department of Engineering Science and Mechanics

Interim Report Number 9

NASA VPI&SU Cooperative Program in Composite  
Materials Research and Education

NASA Grant NGR-47-004-129

Prepared for: Materials Application Branch  
National Aeronautics & Space Administration  
Langley Research Center  
Hampton, VA. 23665

<sup>1</sup> Graduate Student

<sup>2</sup> Professor

Approved for public release, distribution unlimited

## ABSTRACT

Results are obtained for 2-D hygroscopic diffusion into composite laminates with free edges through the use of a second order finite difference scheme. A computer program was developed for the transient nonlinear coupled hygrothermal diffusion into finite width laminates with varying surface conditions along two edges. The formulation permits the diffusion coefficient to be a function of temperature, moisture concentration, and fiber orientation. The moisture distributions thus obtained are necessary for analysis of the moisture induced interlaminar stresses in the vicinity of free edges. It is shown that large diffusion times tend to eliminate the significance of stacking sequence, but gradients within and between layers are significant for all diffusion times.

|                                                                                                                                                                                                      |                              |                                                     |                              |
|------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------|------------------------------|-----------------------------------------------------|------------------------------|
| <b>BIBLIOGRAPHIC DATA SHEET</b>                                                                                                                                                                      | 1. Report No.<br>VPI-E-77-20 | 2.                                                  | 3. Recipient's Accession No. |
| 4. Title and Subtitle<br>TWO-DIMENSIONAL HYGROTHERMAL DIFFUSIONS INTO A FINITE WIDTH COMPOSITE LAMINATE                                                                                              |                              | 5. Report Date<br>June, 1977                        |                              |
|                                                                                                                                                                                                      |                              | 6.                                                  |                              |
| 7. Author(s)<br>Gary L. Farley and Carl T. Herakovich                                                                                                                                                |                              | 8. Performing Organization Rept. No.<br>VPI-E-77-20 |                              |
| 9. Performing Organization Name and Address<br>Virginia Polytechnic Institute and State University<br>Engineering Science and Mechanics<br>Blacksburg, Virginia 24061                                |                              | 10. Project/Task/Work Unit No.                      |                              |
|                                                                                                                                                                                                      |                              | 11. Contract/Grant No.<br>NASA NGR-47-004-129       |                              |
| 12. Sponsoring Organization Name and Address<br>National Aeronautics & Space Administration<br>Langley Research Center<br>Hampton, Virginia 23665                                                    |                              | 13. Type of Report & Period Covered                 |                              |
|                                                                                                                                                                                                      |                              | 14.                                                 |                              |
| 15. Supplementary Notes                                                                                                                                                                              |                              |                                                     |                              |
| 16. Abstracts<br><br>See page ii                                                                                                                                                                     |                              |                                                     |                              |
| 17. Key Words and Document Analysis. 17a. Descriptors<br><br>composite laminate, moisture diffusion, finite difference, free edges, two-dimensional, hygrothermal, stacking sequence, graphite-epoxy |                              |                                                     |                              |
| 17b. Identifiers/Open-Ended Terms                                                                                                                                                                    |                              |                                                     |                              |
| 17c. COSATI Field Group                                                                                                                                                                              |                              |                                                     |                              |
| 18. Availability Statement<br>Distribution unlimited                                                                                                                                                 |                              | 19. Security Class (This Report)<br>UNCLASSIFIED    | 21. No. of Pages             |
|                                                                                                                                                                                                      |                              | 20. Security Class (This Page)<br>UNCLASSIFIED      | 22. Price                    |

**INSTRUCTIONS FOR COMPLETING FORM NTIS-35**

(Bibliographic Data Sheet based on COSATI

Guidelines to Format Standards for Scientific and Technical Reports Prepared by or for the Federal Government, PB-180 600).

1. **Report Number.** Each individually bound report shall carry a unique alphanumeric designation selected by the performing organization or provided by the sponsoring organization. Use uppercase letters and Arabic numerals only. Examples FASEB-NS-73-87 and FAA-RD-73-09.
2. **Leave blank.**
3. **Recipient's Accession Number.** Reserved for use by each report recipient.
4. **Title and Subtitle.** Title should indicate clearly and briefly the subject coverage of the report, subordinate subtitle to the main title. When a report is prepared in more than one volume, repeat the primary title, add volume number and include subtitle for the specific volume.
5. **Report Date.** Each report shall carry a date indicating at least month and year. Indicate the basis on which it was selected (e.g., date of issue, date of approval, date of preparation, date published).
6. **Performing Organization Code.** Leave blank.
7. **Author(s).** Give name(s) in conventional order (e.g., John R. Doe, or J. Robert Doe). List author's affiliation if it differs from the performing organization.
8. **Performing Organization Report Number.** Insert if performing organization wishes to assign this number.
9. **Performing Organization Name and Mailing Address.** Give name, street, city, state, and zip code. List no more than two levels of an organizational hierarchy. Display the name of the organization exactly as it should appear in Government indexes such as Government Reports Index (GRI).
10. **Project/Task/Work Unit Number.** Use the project, task and work unit numbers under which the report was prepared.
11. **Contract/Grant Number.** Insert contract or grant number under which report was prepared.
12. **Sponsoring Agency Name and Mailing Address.** Include zip code. Cite main sponsors.
13. **Type of Report and Period Covered.** State interim, final, etc., and, if applicable, inclusive dates.
14. **Sponsoring Agency Code.** Leave blank.
15. **Supplementary Notes.** Enter information not included elsewhere but useful, such as: Prepared in cooperation with . . . Translation of . . . Presented at conference of . . . To be published in . . . Supersedes . . . Supplements . . . Cite availability of related parts, volumes, phases, etc. with report number.
16. **Abstract.** Include a brief (200 words or less) factual summary of the most significant information contained in the report. If the report contains a significant bibliography or literature survey, mention it here.
17. **Key Words and Document Analysis.** (a). **Descriptors.** Select from the Thesaurus of Engineering and Scientific Terms the proper authorized terms that identify the major concept of the research and are sufficiently specific and precise to be used as index entries for cataloging.  
(b). **Identifiers and Open-Ended Terms.** Use identifiers for project names, code names, equipment designators, etc. Use open-ended terms written in descriptor form for those subjects for which no descriptor exists.  
(c). **COSATI Field/Group.** Field and Group assignments are to be taken from the 1964 COSATI Subject Category List. Since the majority of documents are multidisciplinary in nature, the primary Field/Group assignment(s) will be the specific discipline, area of human endeavor, or type of physical object. The application(s) will be cross-referenced with secondary Field/Group assignments that will follow the primary posting(s).
18. **Distribution Statement.** Denote public releasability, for example "Release unlimited", or limitation for reasons other than security. Cite any availability to the public, other than NTIS, with address, order number and price, if known.
- 19 & 20. **Security Classification.** Do not submit classified reports to the National Technical Information Service.
21. **Number of Pages.** Insert the total number of pages, including introductory pages, but excluding distribution list, if any.
22. **NTIS Price.** Leave blank.

## INTRODUCTION

Problems associated with combined thermal and moisture effects in polymeric matrix composite materials are currently receiving considerable attention on the part of the materials research community. The experimental works of McKague et al [1] and Browning et al [2,3] have shown that there is a degrading effect on the shear, compression and transverse stress properties of resinous composites due to moisture absorption. These degrading effects are primarily due to changes in properties of the resinous matrix and the fiber-matrix interface. McKague et al also presented rather extensive experimental results showing that the rate of moisture absorption is temperature dependent with the rate of absorption increasing with increasing temperature. It was also shown in reference [3] that large moisture concentration gradients may exist near the surfaces of composite laminates. These gradients may be significant because of the possibility of large inter-laminar stresses near the free edge of composite laminates.

Analytical treatments of moisture diffusion in composites have been presented by several authors. Shen and Spring [4] considered one-dimensional absorption and desorption of homogeneous materials and composites, and Whitney [5] considered three-dimensional moisture diffusion in laminated composites. The emphasis in both of the above papers was on the total percent moisture weight gain as a function of time. Whitney also presented moisture profiles for two-dimensional diffusion into a laminate. These profiles were generated assuming the diffusion coefficient was an averaging of the laminates constituents. Since edge effects were included through a correction factor and were

not treated explicitly in either of these two later papers, the significance of laminate stacking sequence wasn't readily assessable.

This paper presents numerical results for two-dimensional moisture diffusion into a symmetric finite width composite laminate. The results were obtained from a recently developed finite difference computer capability, denoted HYDIP, and the associated graphics program HYDIPG. This program was developed for the two-dimensional solution of the transient nonlinear coupled hygrothermal diffusion into a symmetric finite width composite laminate with varying surface conditions along two edges. The moisture distributions thus obtained are necessary for analysis of the interlaminar stresses which may be present in a composite laminate with free edges since these interlaminar stresses often initiate failure.

## 2. PROBLEM FORMULATION

The governing 3-D field equation for hygroscopic or thermal diffusion into a body is given by

$$\frac{\partial}{\partial x} \left( K_x \frac{\partial R}{\partial x} \right) + \frac{\partial}{\partial y} \left( K_y \frac{\partial R}{\partial y} \right) + \frac{\partial}{\partial z} \left( K_z \frac{\partial R}{\partial z} \right) = \frac{\partial R}{\partial t} \quad (1)$$

where  $K_x$ ,  $K_y$  and  $K_z$  represent the diffusion coefficients in the x, y and z directions, respectively, and R is the temperature or moisture concentration at a point in the body. Restricting the problem to that of a finite width symmetric laminate with no variation in the x direction, figure (1), only a quarter laminate need be analyzed. The governing field equation becomes:

$$\frac{\partial}{\partial y} \left( K_y \frac{\partial R}{\partial y} \right) + \frac{\partial}{\partial z} \left( K_z \frac{\partial R}{\partial z} \right) = \frac{\partial R}{\partial t} \quad (2)$$



with symmetry boundary conditions

$$\left. \frac{\partial R}{\partial z} \right|_{z=0} = 0; \left. \frac{\partial R}{\partial y} \right|_{y=0} = 0 \quad (3)$$

and variable surface conditions

$$R = R(z) \Big|_{y=b}; R = R(y) \Big|_{z=H}. \quad (4)$$

More specifically for the case of hygroscopic diffusion, the diffusion coefficient  $D$  may be a function of temperature  $T(y,z)$ , moisture concentration  $M(y,z)$  and lamina fiber orientation  $\theta$ ,

$$D = D(T(y,z), M(y,z), \theta).$$

The governing field equations, (2) - (4), can now be written as

$$\frac{\partial D}{\partial y} \frac{\partial M}{\partial y} + D \frac{\partial^2 M}{\partial y^2} + \frac{\partial D}{\partial z} \frac{\partial M}{\partial z} + D \frac{\partial^2 M}{\partial z^2} = \frac{\partial M}{\partial t} \quad (5)$$

with symmetry boundary conditions

$$\left. \frac{\partial M}{\partial z} \right|_{z=0} = 0; \left. \frac{\partial M}{\partial y} \right|_{y=0} = 0 \quad (6)$$

and variable surface conditions

$$M = M(z) \Big|_{y=b}; M = M(y) \Big|_{z=H}. \quad (7)$$

### 3. SOLUTION SCHEME

The solution of the diffusion equation (5) was performed by a second order accurate variable step size finite difference scheme [6]. First and second derivative central difference derivatives are employed in the interior region of the laminate while only first derivative

forward difference derivatives are necessary along the symmetry boundary conditions. A complete presentation of the basic difference equations used and the equivalent difference equation of equations (5) and (6) are presented in Appendix A.

Applying equations (A11) - (A13) at nodes throughout the laminate yields a set of linear simultaneous equations of the form

$$[C_t]\{M_{t+1}\} = \{P_t\} \quad (7)$$

where  $[C_t]$  is the coefficient matrix at time  $t$ ,  $\{M_{t+1}\}$  are the unknown moisture concentration at time  $t+1$  and  $\{P_t\}$  is the right hand side vector which is a function of the moisture concentration at time  $t$ . It should be realized that at  $t = 0$   $\{P_{t=0}\}$  would be a function of the initial moisture distribution. Equation (7) is then successively solved over  $N$  time increments. Transient problems can similarly be solved by imposing transient surface conditions in an incremental fashion.

An iterative simultaneous equation solution scheme [6], though more expensive to use for a single analysis, was chosen over an elimination or decomposition algorithm. This scheme was selected due to the incremental nature of the diffusion problem and because iterative schemes become cost efficient when successive solutions change only slightly from the previous results.

A Gauss-Siedel simultaneous equation solver was modified to efficiently solve equation (7) over  $N$  time intervals. This was primarily achieved by eliminating the storage of zero coefficients and the multiplication by zeros. The required storage locations and multiplications of the modified Gauss-Siedel routine then become linear functions of the number of unknowns. A more detailed discussion of this solution scheme is presented in Appendix B.

#### 4. CASE STUDIES

As mentioned in the introduction, large gradients in moisture concentration may exist near the free surfaces of a laminate. In this study it will be assumed that these gradients are the result of the laminate surface being subjected to an environment different from the one associated with the moisture distribution initially existing in the laminate. This condition could similarly be induced by thermal gradients in the composite as well as a variety of combinations of thermal and moisture distributions.

The initial studies investigated the effect of stacking sequence on the moisture distribution within the boundary layer region, approximately two lamina thicknesses along the laminates free edge. Material diffusion coefficients, [2], used in this study are shown in figure (2) while the laminates investigated are:  $[90_2, 0_2]_s$ ,  $[90, 0_3]_s$ ,  $[0, 90_2, 0]_s$ ,  $[90, 0_2, 90]_s$ ,  $[0_2, 90_2]_s$ ,  $[0, \pm 45, 90]_s$ ,  $[90, \pm 45, 0]_s$ .

Upon examination of the laminates studied it becomes obvious that primarily  $0_N/90_N$  combination laminates were considered. These laminates were chosen because they produce the most dramatic results due to the relative magnitude of the diffusion coefficients. Though the studies were very selective, the program HYDIP will handle any number of layers each at different fiber orientation and each having different material properties.

The basic model was a four layer symmetric laminate with 510 nodes on the model. Each layer, 0.005 in. thick and 1.0 in. wide, contains four nodes through the thickness with an additional node on the upper surface and 30 linearly spaced nodes across the width, Figure (1). The laminate was assumed to be initially dry and at a temperature of 440°K.

This temperature was chosen because the diffusion coefficient was much larger than that at room temperature as seen in Figure (2). An applied surface condition corresponding to 100 percent relative humidity was uniformly distributed along both free surfaces.

The plotted results in figures (3-13) have uniformly spaced nodes and are plotted with a slightly distorted aspect ratio to more readily visualize pertinent trends. As previously mentioned these plots represent a region of approximately two lamina thicknesses from the free edge.

Moisture distribution isoclines are numbered on each plot. Isoclines labeled 6 represent fully saturated conditions while those labeled 1 represents moisture concentrations of  $1/6^{\text{th}}$  the saturated values.

## 5. RESULTS AND CONCLUSIONS

The effect of stacking sequence is most noticable after a short interval, on the order of 2-3 minutes, in a region near the free edge, as shown in Figures (3, 5, 8). This phenomena was typical of all laminates studied but will be shown using selected laminates. Transverse diffusion (z direction) reduces or eliminates the effect of stacking sequence for diffusion times greater than five minutes. This was indicative of all studies performed, especially in the outer region (see Figures (4, 7, 9, 11, 13) of the laminate, but to a lesser extent in the inner region.

Large transverse gradients in moisture concentrations occurred within the outer layers with significant "corner" and "longitudinal" gradients in the adjacent and center most layer in all laminates studied, (Figure 3-13). Moisture diffusion was more uniform, i.e., smaller irregularities, with laminates having lower diffusion rates in the outer

most layer. This is readily seen by comparing the time history contours of the  $[0,\pm45,90]_S$  and  $[90,\pm45,0]_S$  laminates as shown in Figures (10-13).

In conclusion, the stacking sequence was significant for very small diffusion times and in a region near the free edge. However, large diffusion times tended to eliminate the significance of stacking sequence due to the high transverse diffusion rates and aspect ratio of the composite laminate. Moisture concentration gradients within and between layers were significant for all diffusion times. From these results it is expected that large moisture gradients could produce large interlaminar stresses and greatly effect free edge delamination.

## REFERENCES

1. McKague, E. L., Reynolds, J. D., and Halkins, J. E., "Life Assurance of Composite Structures", Vol. 1, AFML-TR-75-51, 1975.
2. Browning, C. E., Husman, G. E., and Whitney, J. M., "Moisture Effects in Epoxy Matrix Composites", Composite Materials: Testing and Design (Third Conference), ASTM STP 546, Am. Soc. for Testing and Materials, 1974, pp. 284-302.
3. Shirrell, C. S., Halpin, J. C., Browning, C. E., "Moisture- An Assessment of Its Impact on the Design of Resin Based Advanced Composites", 3rd Annual Conf. on Fiber Composites in Flight Vehicle Design, Williamsburg, VA., Nov. 1975.
4. Shen, C. H., and Springer, G. S., "Moisture Absorption and Desorption of Composite Materials", J. Comp. Materials, Vol. 10 (January, 1976) p. 2.
5. Whitney, J. M., "Three-Dimensional Moisture Diffusion in Laminated Composites", AIAA/ASME, 18th Structures, Structural Dynamics and Materials Conference, San Diego, March, 1977.
6. Ketter, R. L. and Prawel, S. P., Modern Methods of Engineering Computation, McGraw-Hill, 1969.

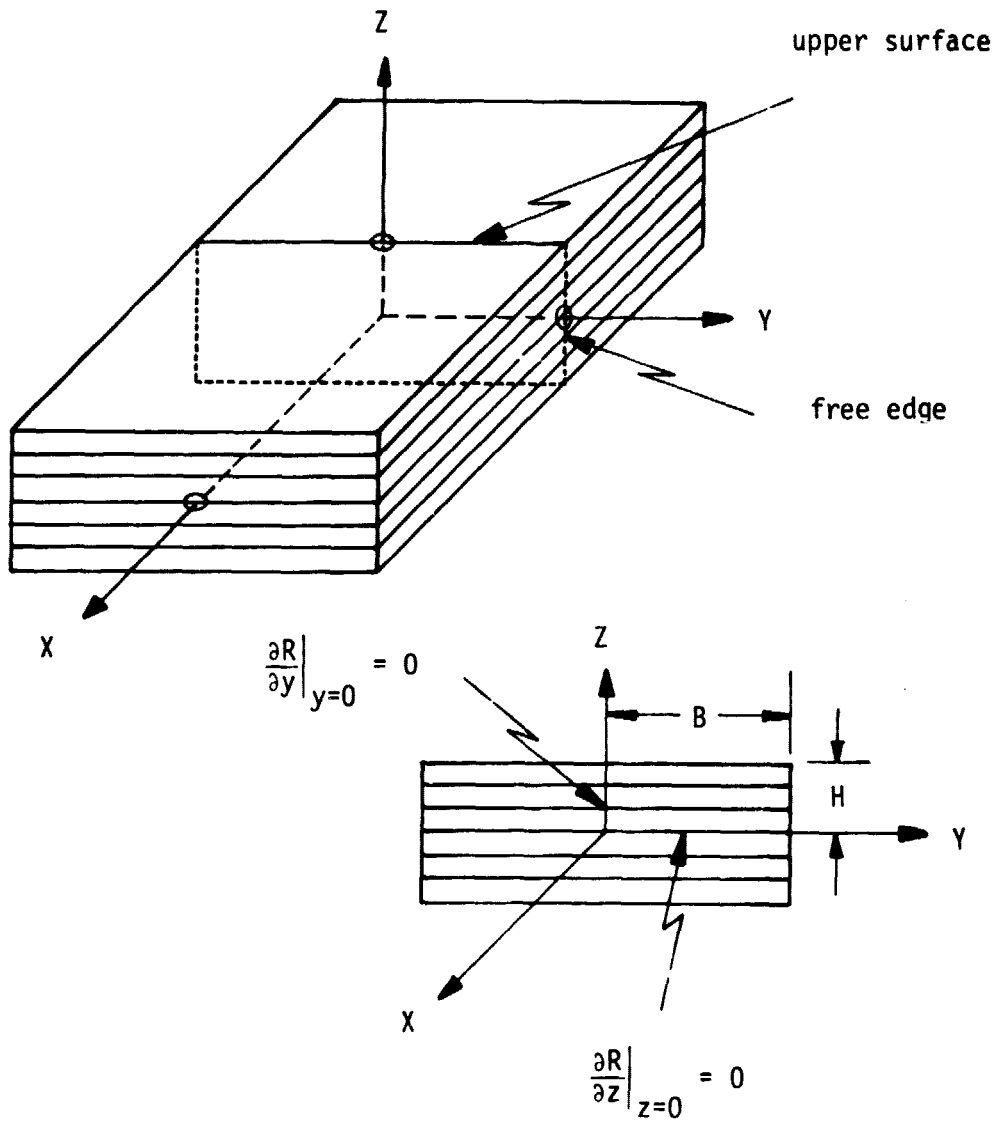


Figure (1) Symmetric Laminate with Boundary Conditions

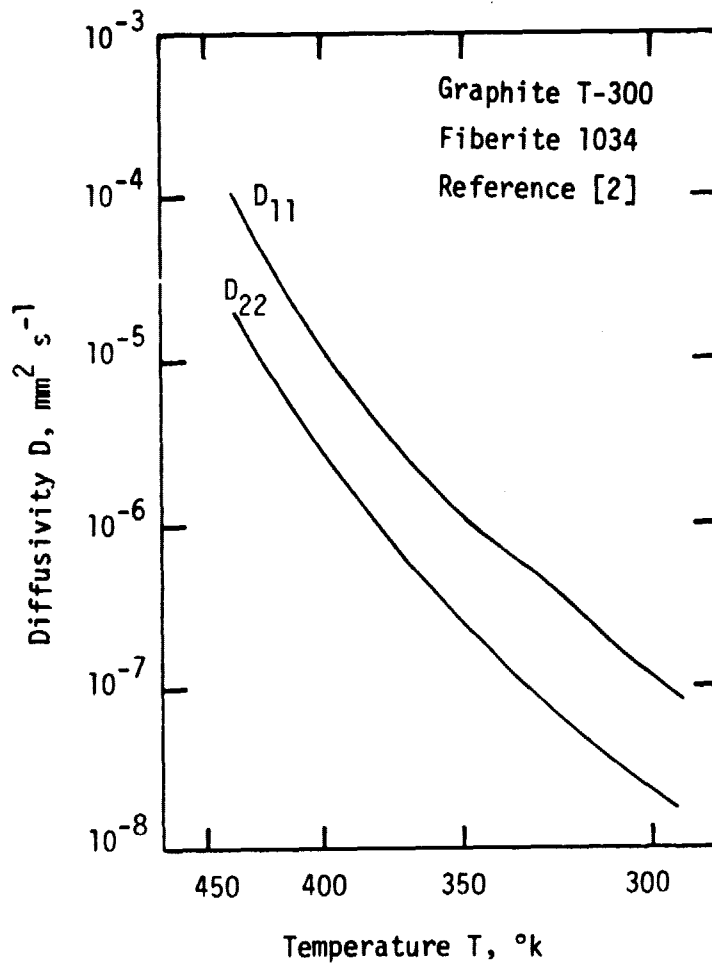


Figure (2) Longitudinal and Transverse Diffusion Coefficients vs. Temperature ( $^{\circ}\text{K}$ )



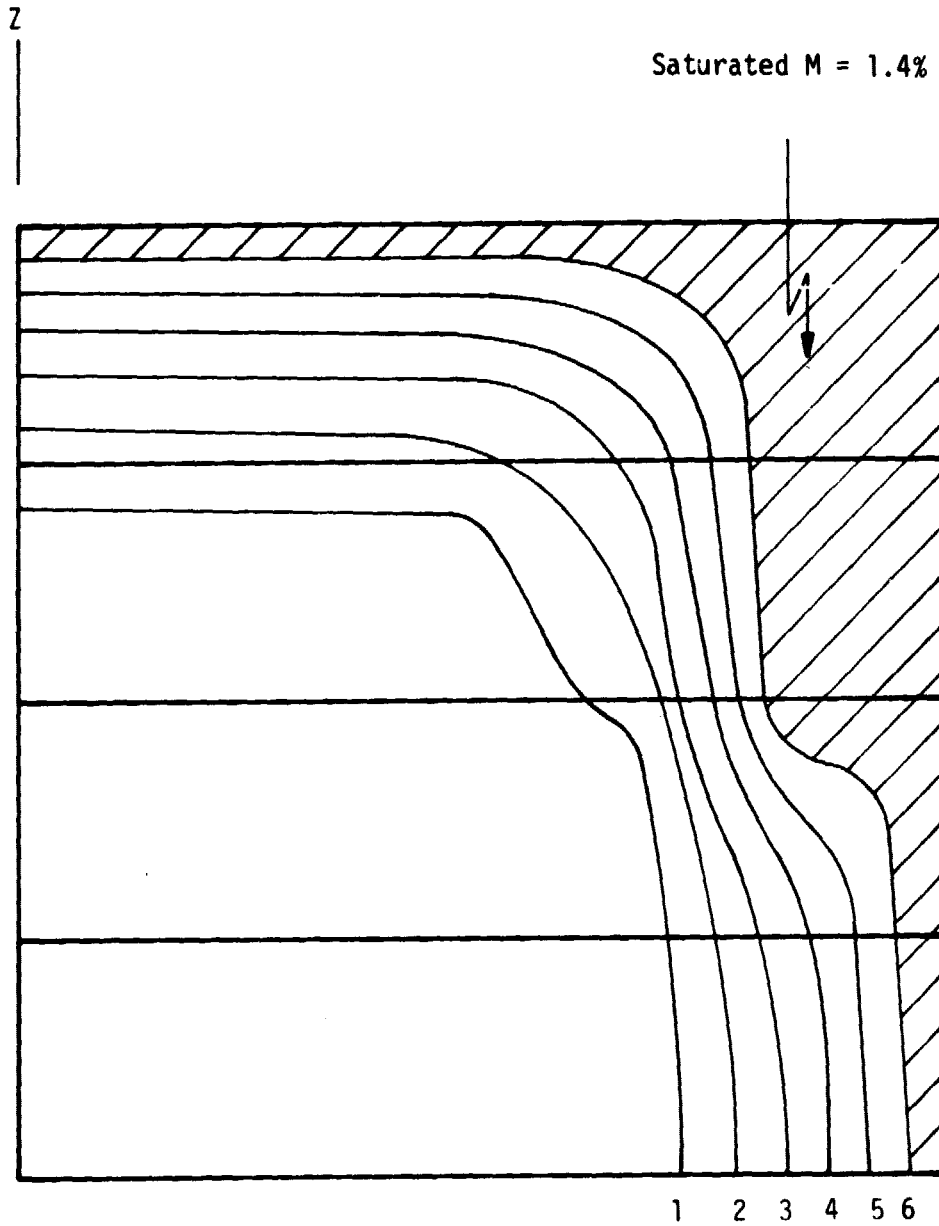


Figure (3) Moisture Concentration Contours in a  $[90_2, 0_2]_s$  Laminate at  $t = 150$  sec.

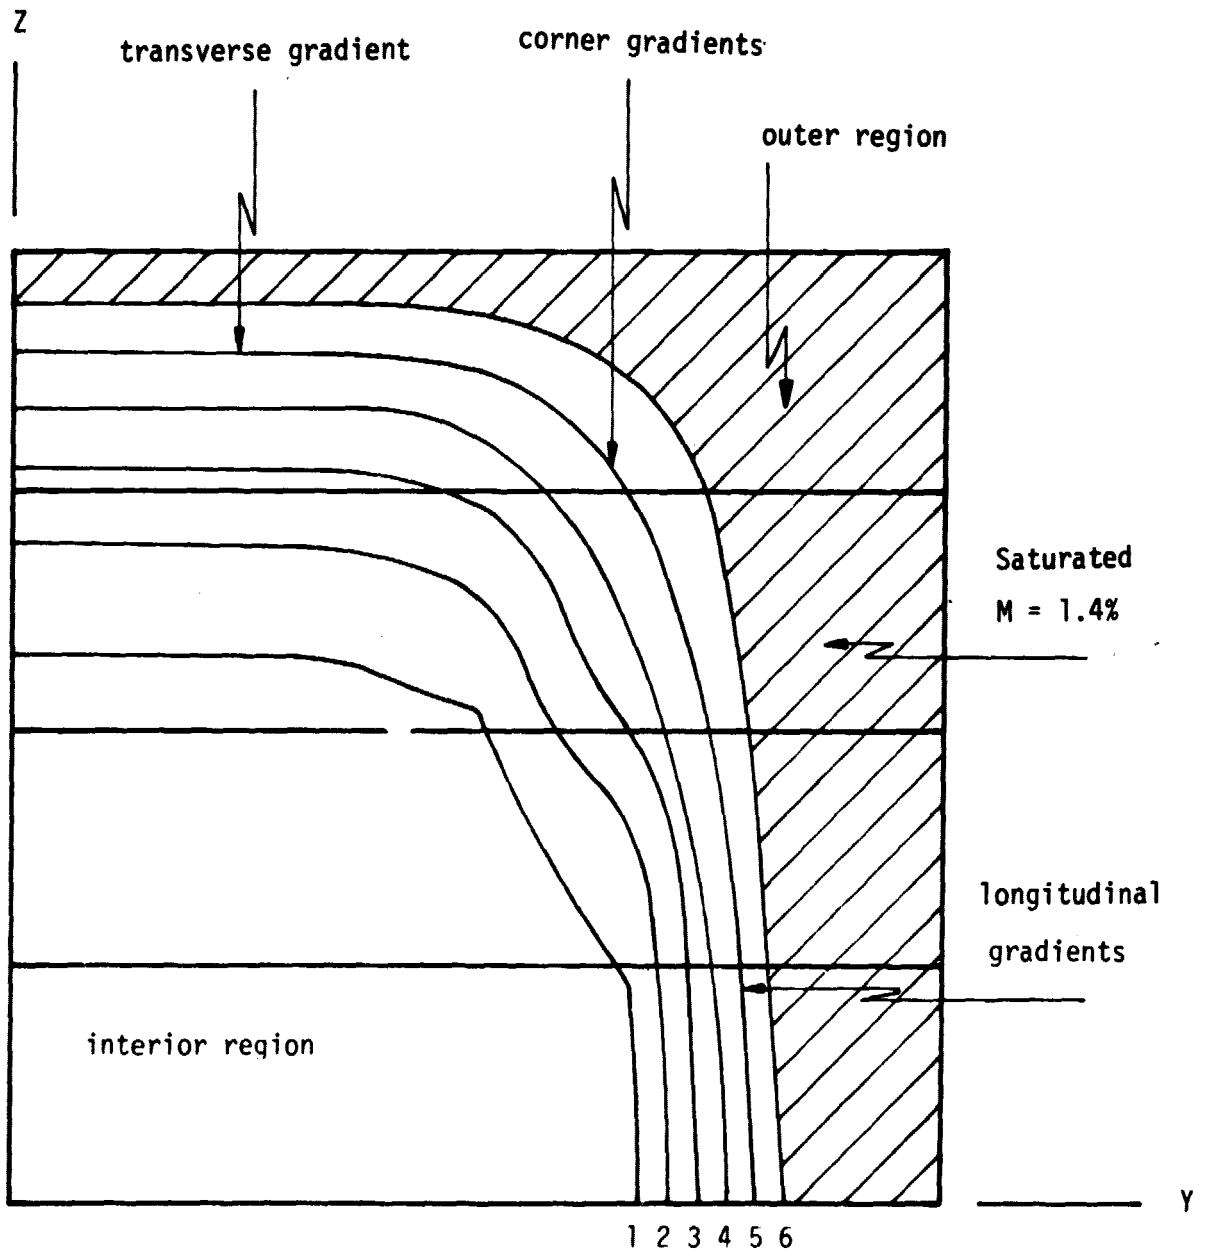


Figure (4) Moisture Concentration Contours in a  $[90_2 0_2]_s$  Laminate at  $t = 300$  sec.

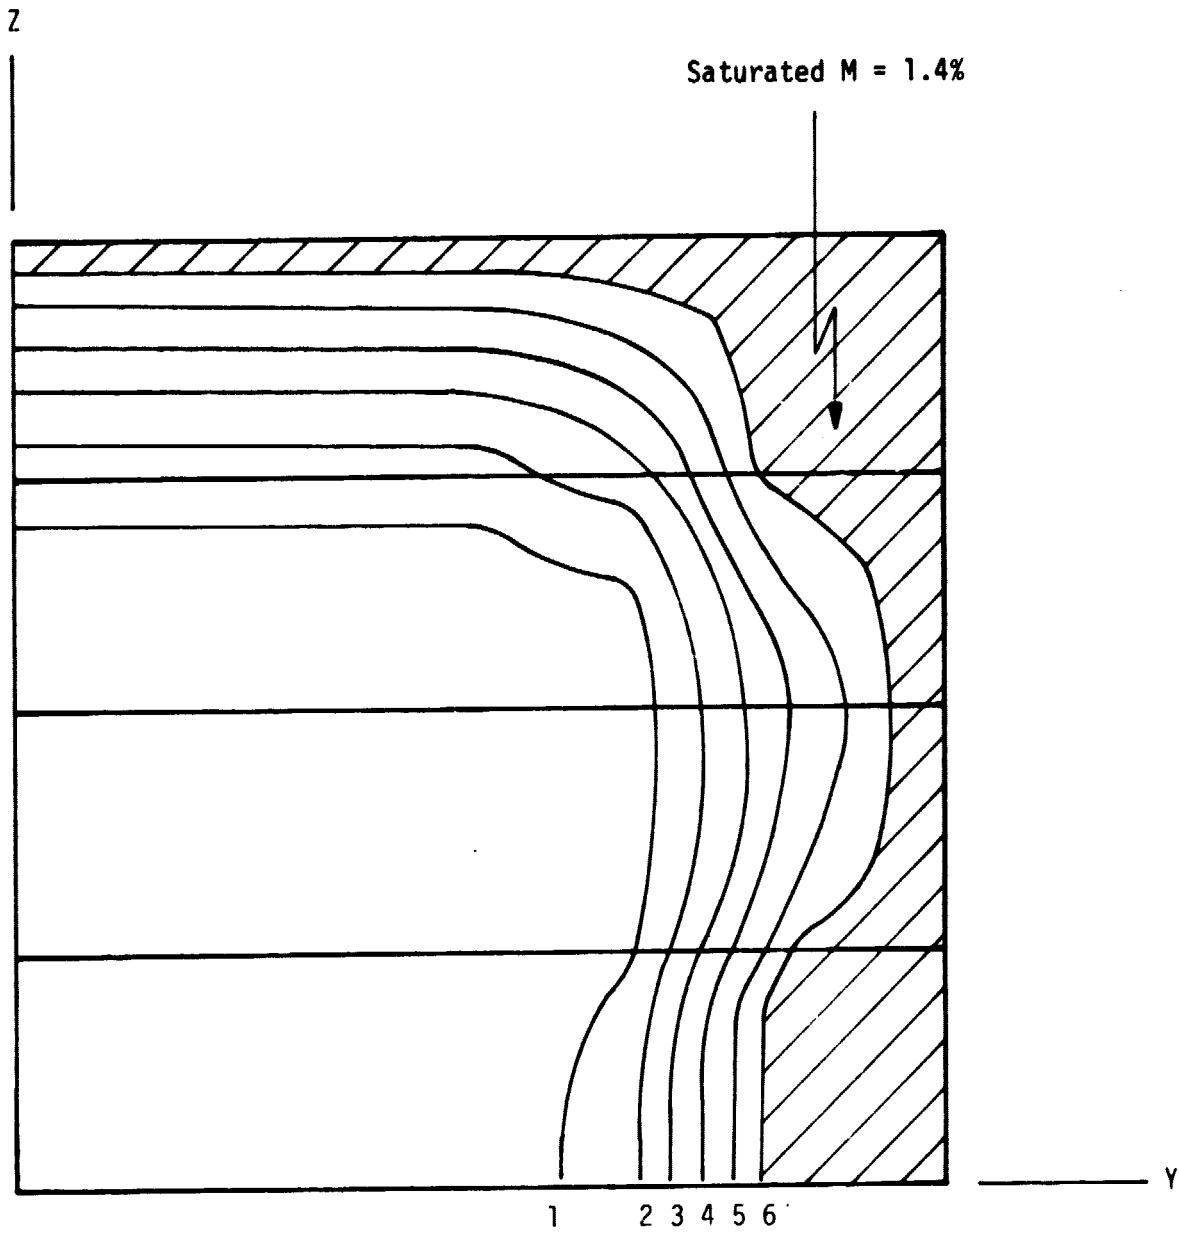


Figure (5) Moisture Concentration Contours in a  $[90,0_2,90]_s$  Laminate at  $t = 150$  sec.

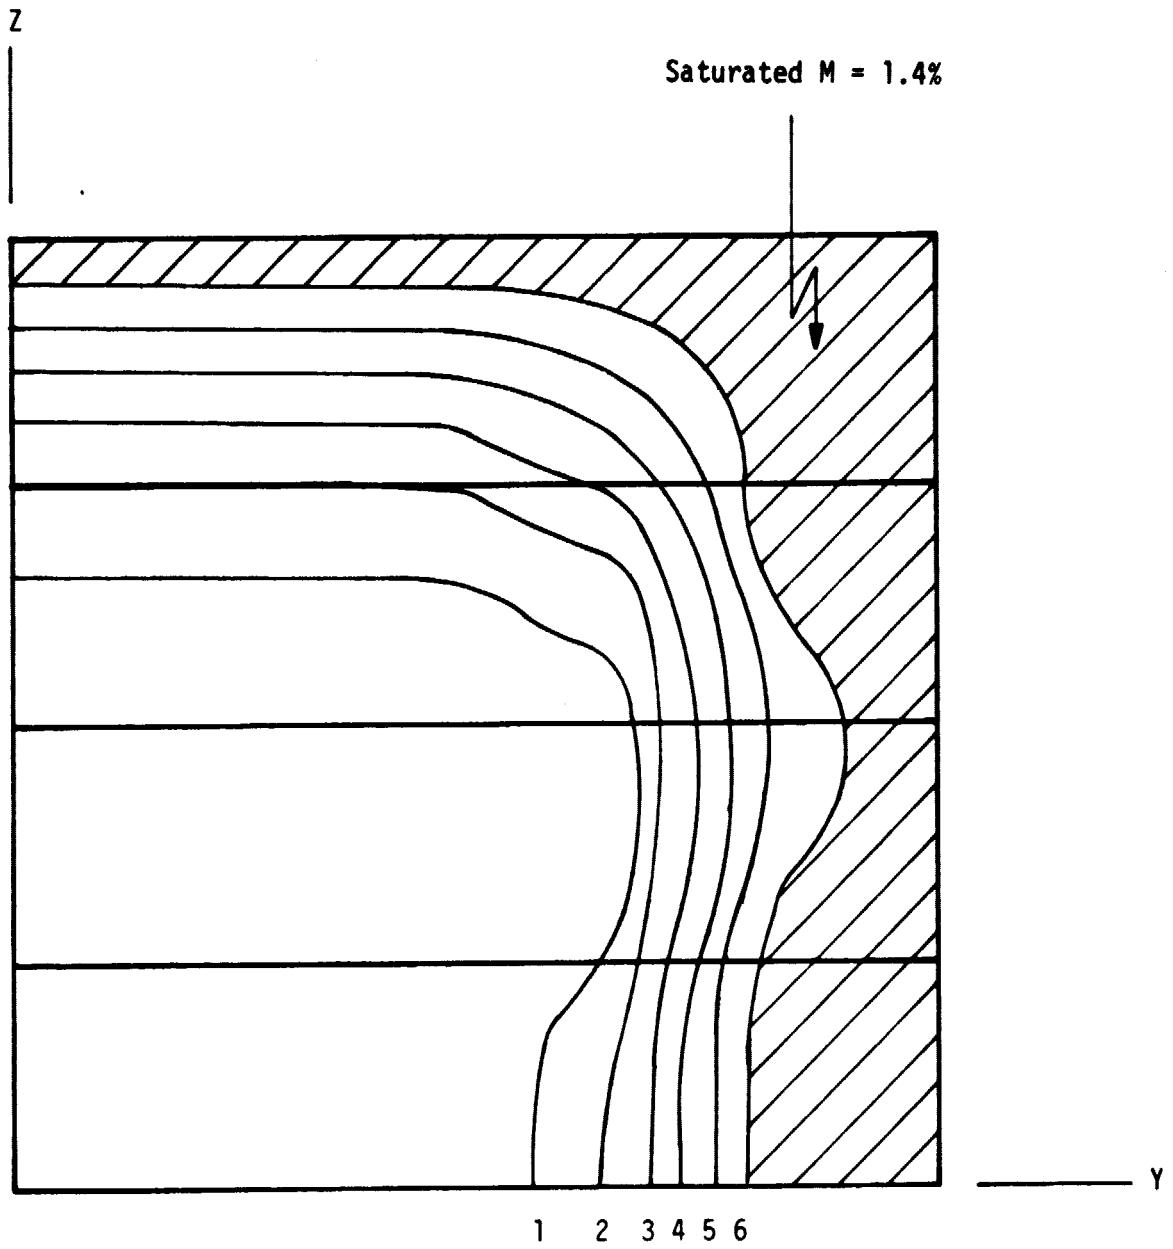


Figure (6) Moisture Concentration Contours in a  $[90,0_2,90]_s$  Laminate at  $t = 200$  sec.

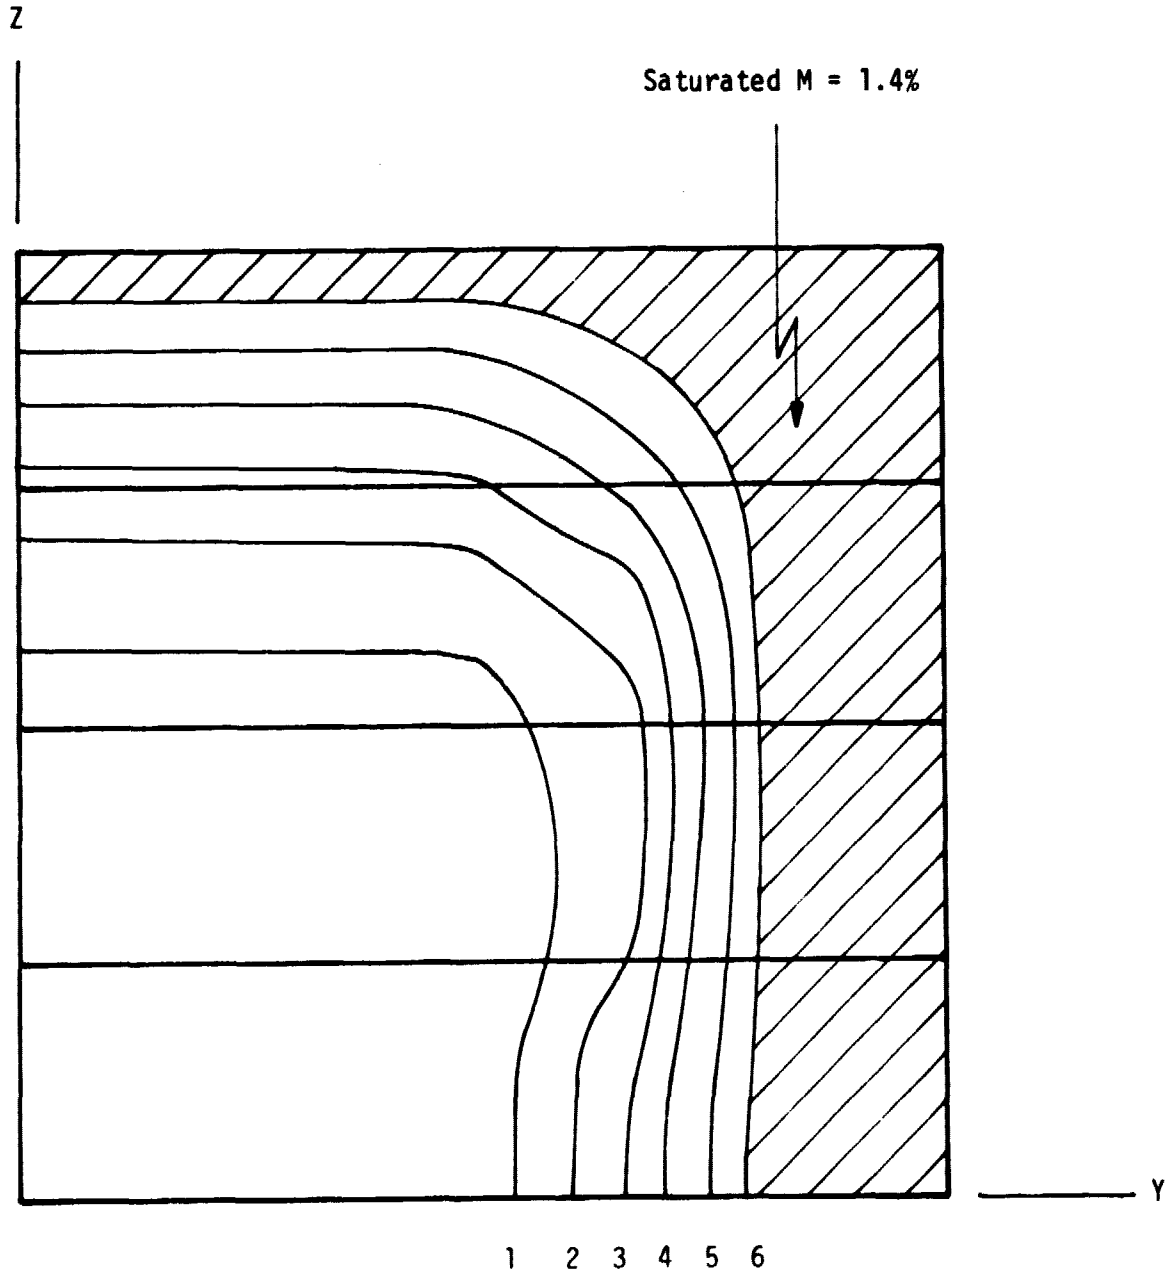


Figure (7) Moisture Concentration Contours in a  $[90,0_2,90]_s$  Laminate at  $t = 300$  sec.

Z

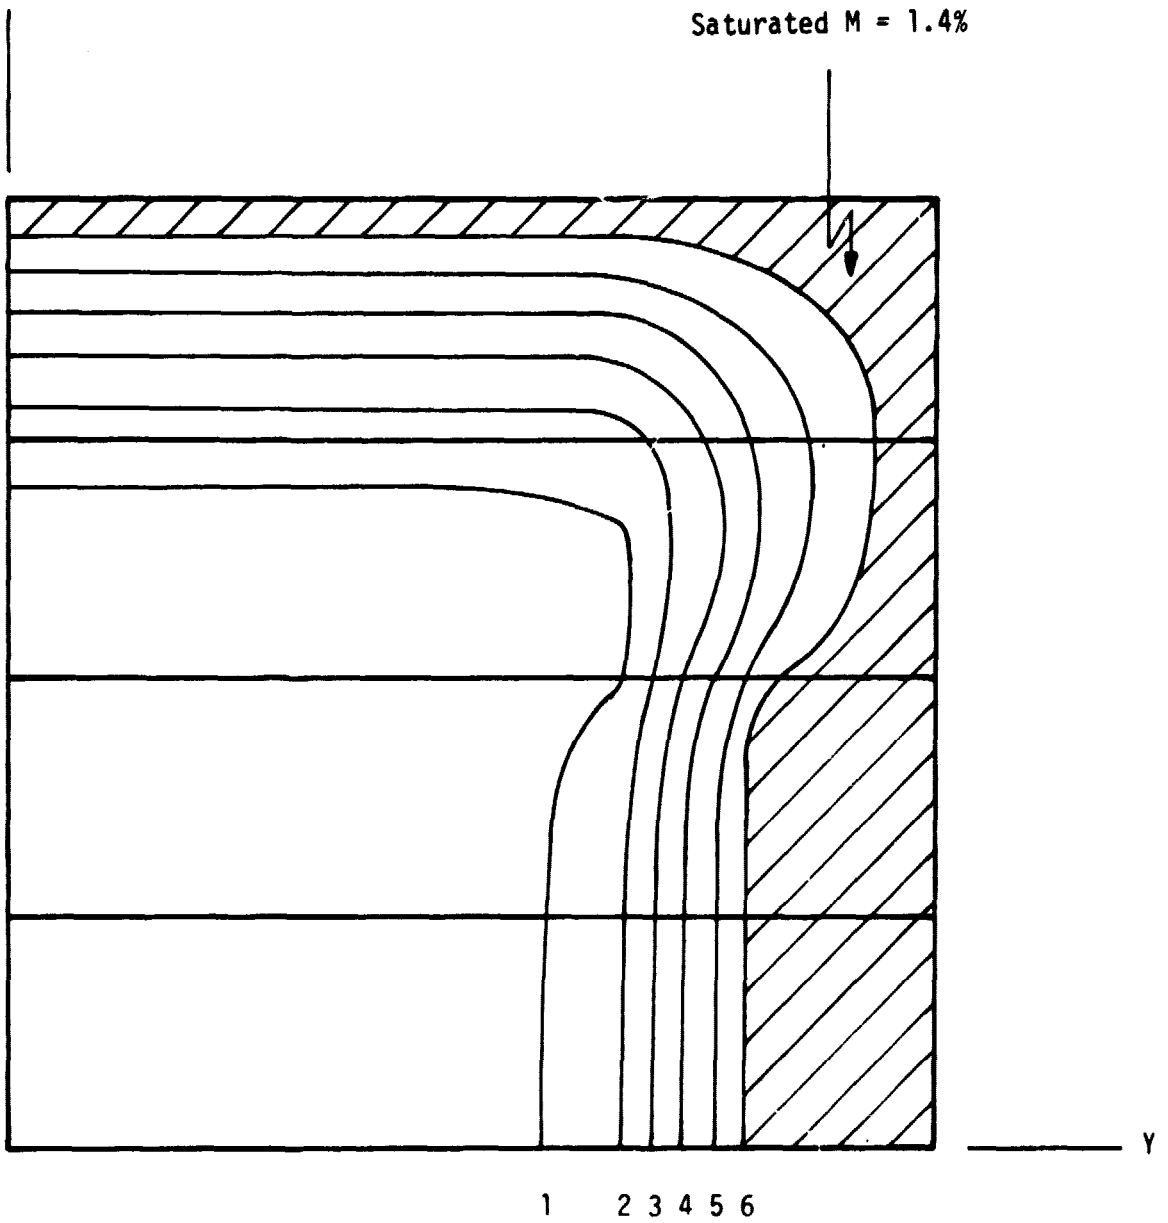


Figure (8) Moisture Concentration Contours in a  $[0_2, 90_2]_s$  Laminate at  $t = 150$  sec.

Z

Saturated M = 1.4%

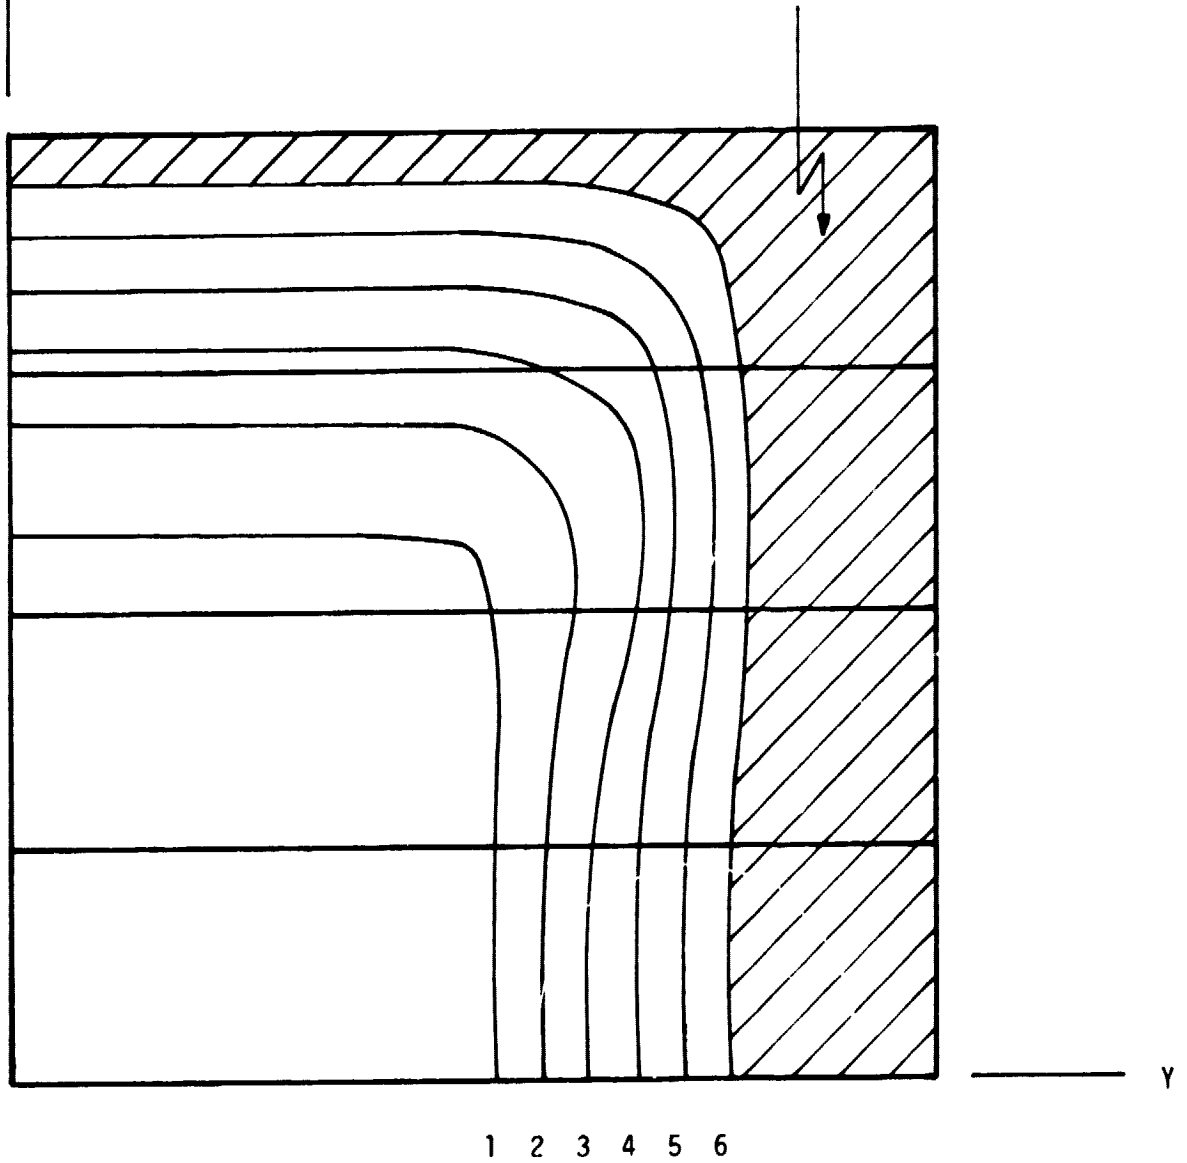


Figure (9) Moisture Concentration Contours in a  $[0_2, 90_2]_s$  Laminate at  $t = 300$  sec.

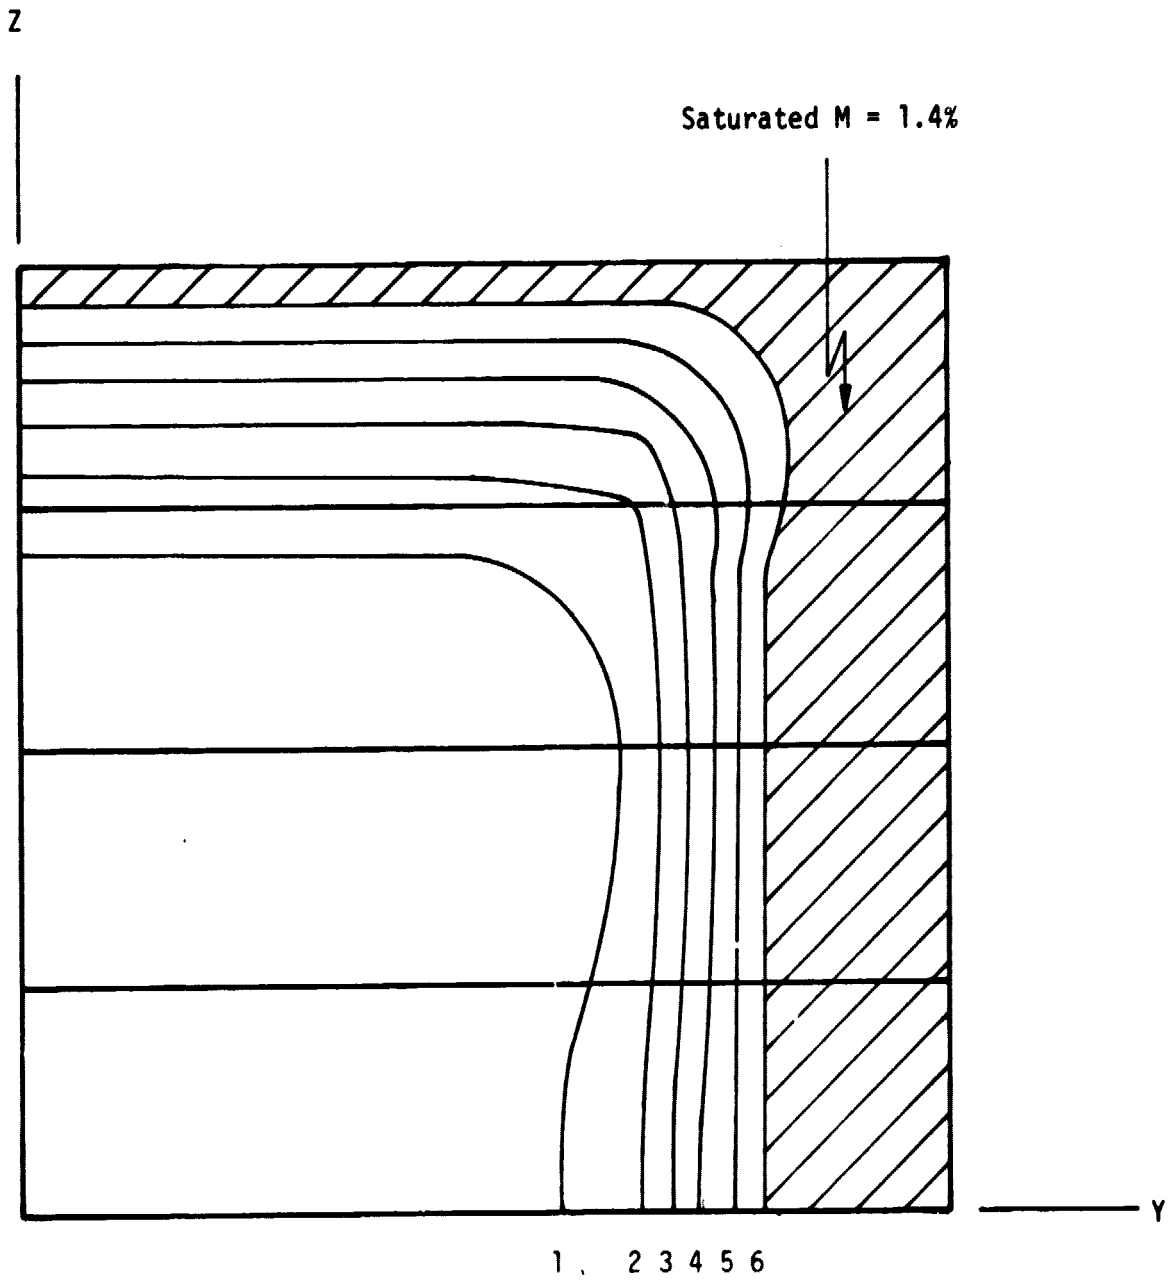


Figure (10) Moisture Concentration Contours in a  $[0, \pm 45, 90]_s$  Laminate at  $t = 150$  sec.



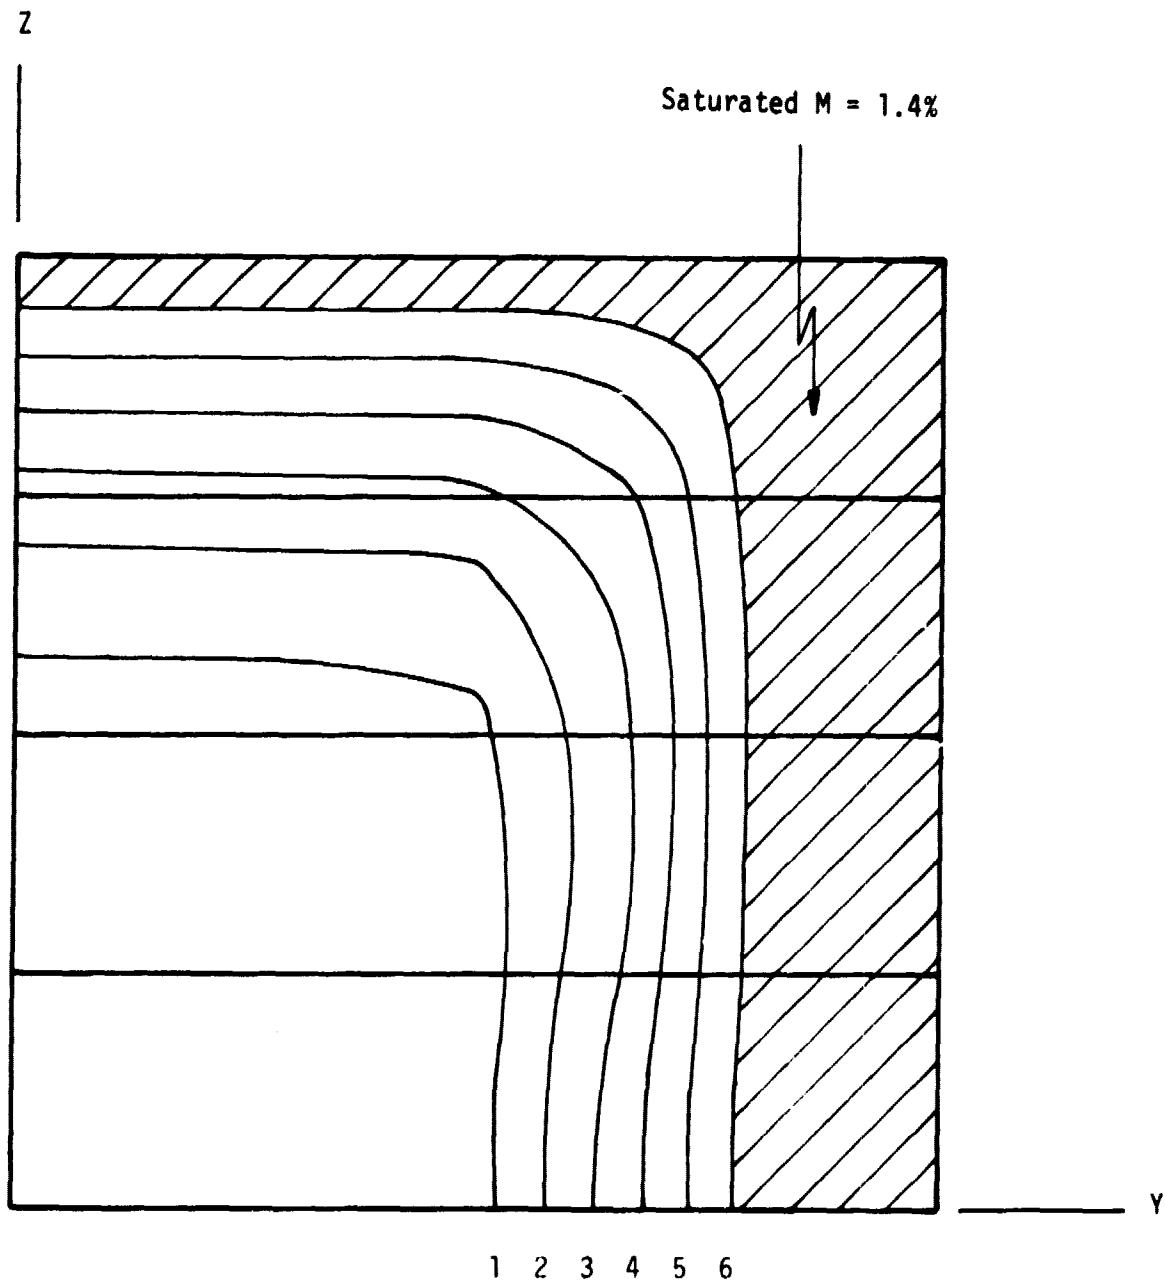


Figure (11) Moisture Concentration Contours in a  $[0, \pm 45, 90]_s$  laminate at  $t = 300$  sec.

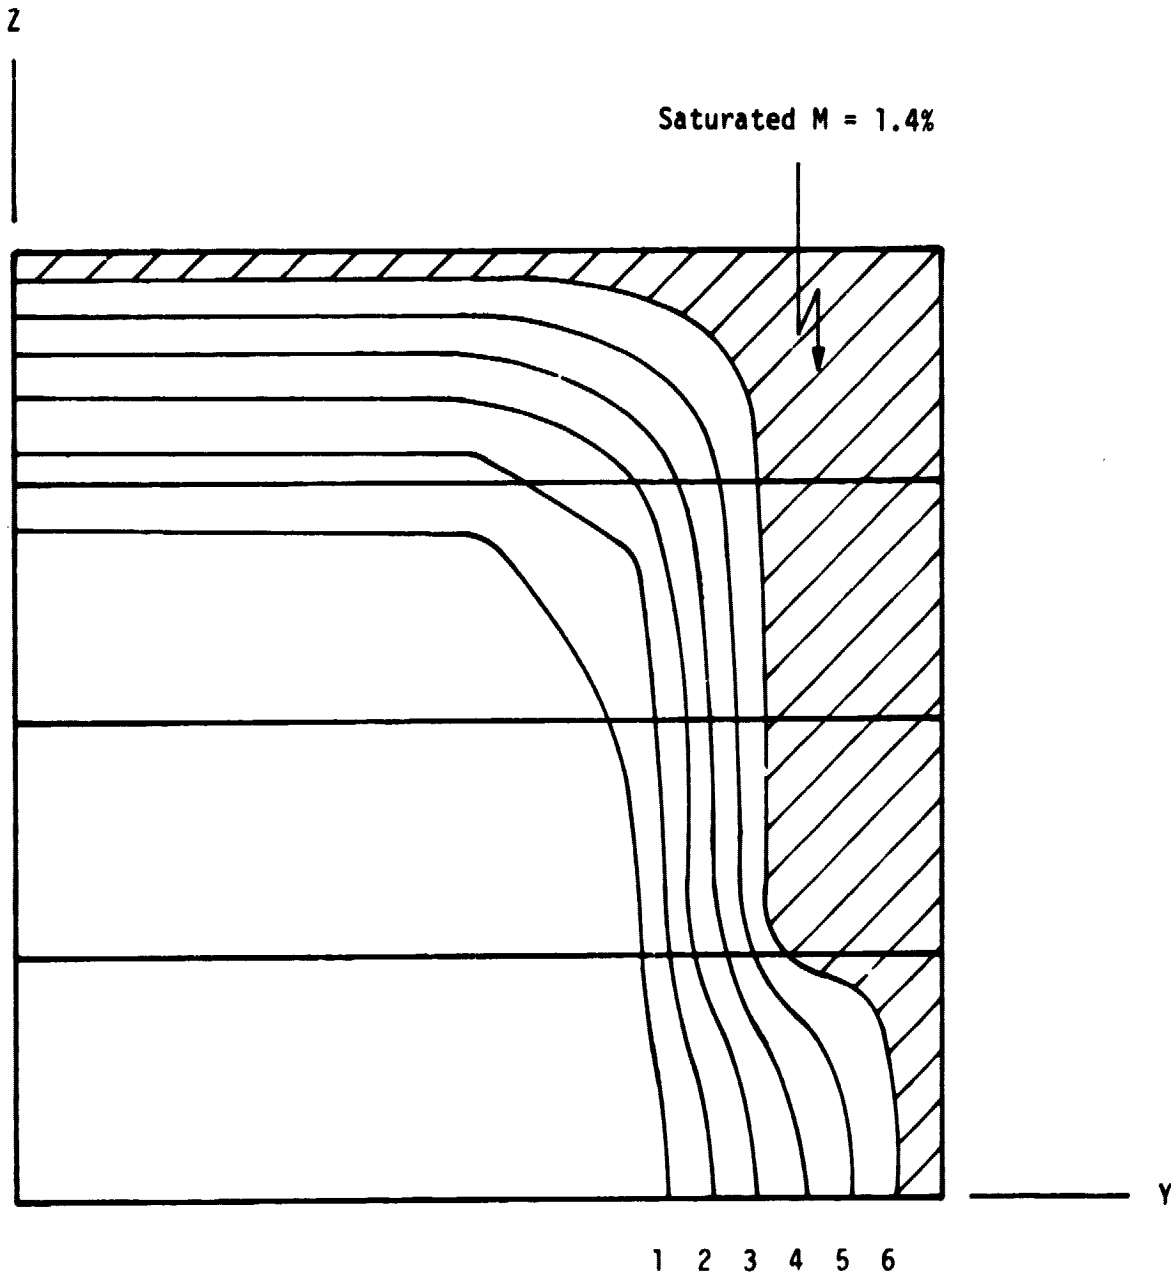


Figure (12) Moisture Concentration Contours in a  $[90, \pm 450]_s$  Laminate at  $t = 150$  sec.

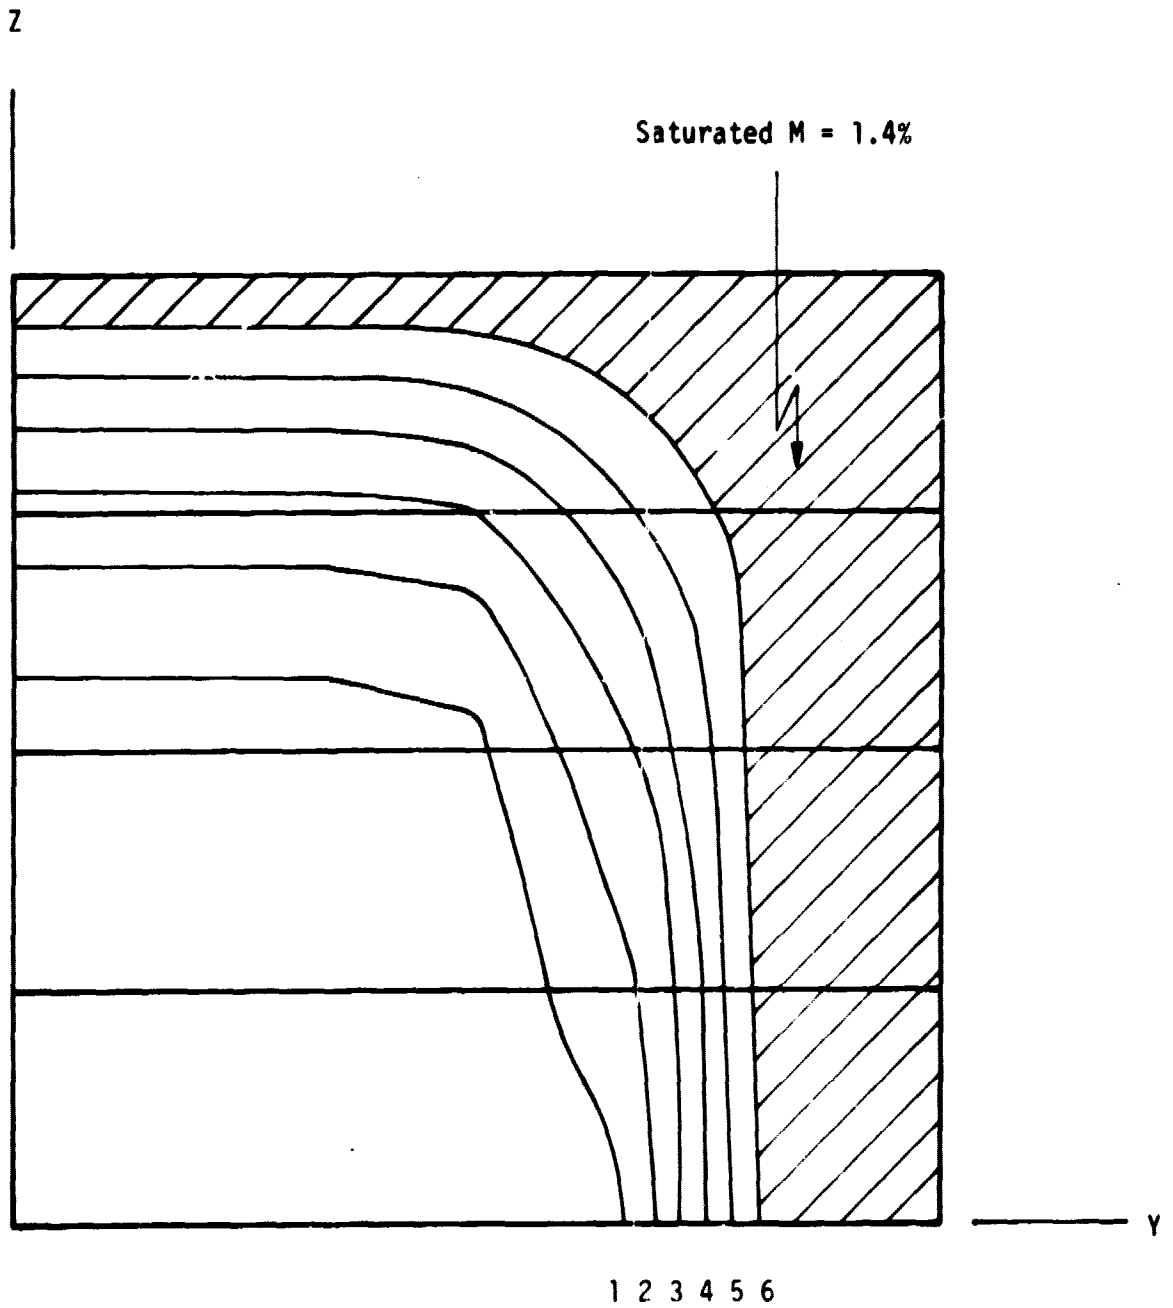


Figure (13) Moisture Concentration Contours in a  $[90, \pm 45, 0]_S$  Laminate at  $t = 300$  sec.

## APPENDIX A

The finite difference derivatives were developed from a second order polynomial with unequal nodal spacing. The coefficients of the second order polynomial, (A1),

$$y = a_2x^2 + a_1x + a_0 \quad (A1)$$

can be determined by knowing the magnitude of  $y$  at three discrete points,  $x_0, x_1, x_2$ . Substituting these values of  $x$  and  $y$  into the polynomial, the  $a_i$ 's can be determined through the matrix equation (A2).

$$\begin{bmatrix} 1 & 0 & 0 \\ 1 & h & h^2 \\ 1 & h(1+\alpha) & h^2(1+\alpha)^2 \end{bmatrix} \begin{Bmatrix} a_0 \\ a_1 \\ a_2 \end{Bmatrix} = \begin{Bmatrix} y_0 \\ y_1 \\ y_2 \end{Bmatrix} \quad (A2)$$

where

$$h \equiv x_1 - x_0$$

$$\alpha \equiv (x_2 - x_1)/(x_1 - x_0)$$

The first derivative at  $x = x_0$  in terms of  $h, \alpha, y_0, y_1$ , and  $y_2$  is;

$$D(y_0) = -\frac{y_0(\alpha+2)}{h(1+\alpha)} + \frac{y_1(1+\alpha)}{h\alpha} - \frac{y_2}{h\alpha(1+\alpha)} \quad (A3)$$

In a similar fashion the first and second central difference derivatives are;

$$D(y_0) = \frac{1}{h} \left[ -\frac{\alpha y_1}{(1+\alpha)} + \frac{(1-\alpha)y_0}{\alpha} + \frac{y_1}{\alpha(1+\alpha)} \right] \quad (A4)$$

$$D^2(y_0) = \frac{2}{h^2} \left[ \frac{y_{-1}}{(1+\alpha)} - \frac{y_0}{\alpha} + \frac{y_1}{\alpha(1+\alpha)} \right] \quad (A5)$$

Substituting equations (A4) and (A5) into (5) yields;

$$\begin{aligned} & \frac{1}{h^2_{i,j}} \left[ \frac{-\alpha_{i,j} D_{y_{i-1,j,t}}}{(1+\alpha_{i,j})} + \frac{(1-\alpha_{i,j})}{\alpha_{i,j}} D_{y_{i,j,t}} + \frac{D_{y_{i+1,j,t}}}{\alpha_{i,j}(1+\alpha_{i,j})} \right] \\ & * \left[ \frac{-\alpha_{i,j} M_{i-1,j,t+1}}{(1+\alpha_{i,j})} + \frac{(1-\alpha_{i,j})}{\alpha_{i,j}} M_{i,j,t+1} + \frac{M_{i+1,j,t+1}}{\alpha_{i,j}(1+\alpha_{i,j})} \right] \\ & + \frac{1}{k^2_{i,j}} \left[ \frac{-\beta_{i,j} D_{z_{i,j-1,t}}}{(1+\beta_{i,j})} + \frac{(1-\beta_{i,j})}{\beta_{i,j}} D_{z_{i,j,t}} + \frac{D_{z_{i,j+1,t}}}{\beta_{i,j}(1+\beta_{i,j})} \right] \\ & * \left[ \frac{-\beta_{i,j} M_{i,j-1,t+1}}{(1+\beta_{i,j})} + \frac{(1-\beta_{i,j})}{\beta_{i,j}} M_{i,j,t+1} + \frac{M_{i,j+1,t+1}}{\beta_{i,j}(1+\beta_{i,j})} \right] \\ & + D_{y_{i,j,t}} * \frac{2}{h^2_{i,j}} \left[ \frac{M_{i-1,j,t+1}}{(1+\alpha_{i,j})} - \frac{M_{i,j,t+1}}{\alpha_{i,j}} + \frac{M_{i+1,j,t+1}}{\alpha_{i,j}(1+\alpha_{i,j})} \right] \\ & + D_{z_{i,j,t}} * \frac{2}{k^2_{i,j}} \left[ \frac{M_{i,j-1,t+1}}{(1+\beta_{i,j})} - \frac{M_{i,j,t+1}}{\beta_{i,j}} + \frac{M_{i,j+1,t+1}}{\beta_{i,j}(1+\beta_{i,j})} \right] \\ & = \frac{1}{2\tau} [M_{i,j,t+1} - M_{i,j,t}] \quad (A6) \end{aligned}$$

with boundary conditions obtained by substituting equation (A3) into

(4). This yields;

$$\frac{-M_{1,j}(\beta_{1,j} + 2)}{(1+\beta_{1,j})} + \frac{M_{2,j}(1+\beta_{1,j})}{\beta_{1,j}} - \frac{M_{3,j}}{\beta_{1,j}(1+\beta_{1,j})} = 0 \quad (A7)$$

along  $z = 0$  where  $i = 1$ , and

$$\frac{-M_{i,1}(\alpha_{i,1} + 2)}{(1 + \alpha_{i,1})} + M_{i,2} \frac{(1 + \alpha_{i,1})}{\alpha_{i,1}} - \frac{M_{i,3}}{\alpha_{i,1}(1 + \alpha_{i,i})} = 0 \quad (A8)$$

along  $y = 0$  where  $j = 1$ .

The coefficients used in equations (A6) - (A8) are defined as;

$M_{i,j}$   $\equiv$  moisture concentration at the  $i,j^{\text{th}}$  node.

$h_{i,j}$   $\equiv$  horizontal step size, (in the  $y$  direction)

$k_{i,j}$   $\equiv$  vertical step size, (in the  $z$  direction)

$D_{y,i,j,t}$   $\equiv$  diffusion coefficient in the  $y$  direction at node  $i,j$   
determined from moisture and temperature data at time  $t$ .

$$D_{y,i,j,t} = D(T,M,Y,Z,\theta) = D_{22} \cos^2 \theta + D_{11} \sin^2 \theta.$$

$D_{11}, D_{22}$   $\equiv$  longitudinal and transverse diffusion constants relative  
to the principal material coordinates.

$D_{z,i,j,t}$   $\equiv$  diffusion constant in the  $z$  direction at the  $i,j^{\text{th}}$  node  
determined from moisture and temperature data at time  $t$ .

In general  $D_z = D_{22}$ .

$\alpha_{i,j}$   $\equiv$  ratio of distance between  $i-1, j-i$  and  $i, j-i+1, j$  nodes.

$\beta_{i,j}$   $\equiv$  ratio of distance between  $i, y-1-i, j$  and  $i, j-i, j+1$   
nodes.

$\tau$   $\equiv$  time increment

## APPENDIX B

The unmodified Gauss Siedel simultaneous equation algorithm to solve equation (7) is of the form

$$\{M_{K+1}\} = \{D\} - [B]\{M_K\} \quad (B1)$$

where

$$D_i = P_i / C_{i,i}$$

$$B_{i,j} = C_{i,j} / C_{i,i} \text{ for } i \neq j$$

$$B_{i,i} = 0, \text{ with } i, j = 1, 2, \dots \text{ number of unknowns (NNUM)}$$

and  $\{M_K\}$  is continuously updated from the computed results of  $\{M_{K+1}\}$ .

This algorithm, as posed, requires storage on the order of  $(\text{NNUM})^2$  and multiplications equal to  $(\text{NNUM})^3$ , per convergence iteration.

Upon formulating the diffusion problem in conjunction with the Gauss Siedel solution scheme there are, at most, four non-zero  $B_{i,j}$  coefficients per row. The number of non-zero coefficients is a function of the order of the difference equation and its order of accuracy. By eliminating the large number of zero coefficients in  $[B]$  and their multiplications the computer resources used to solve this problem would be greatly reduced. This was accomplished by developing only the non-zero  $[B]$  coefficients along with a series of pointer vectors relating them to the appropriate guess solution in vector  $\{M_K\}$ . As coded in HYDIP coefficient storage, including pointer vectors, is

9\*(NNUM) locations while multiplications per convergence iteration equals 4\*(NNUM).

Table (B1) presents a comparison of required computer resources to solve the diffusion problem using the modified Gauss Siedel, unmodified Gauss Siedel and a non-banded or blocked out of core Gaussian elimination algorithms. As seen from the table, the required computer resources varies linearly with respect to the number of unknowns for the modified Gauss Siedel algorithm while the other methods are quadratic or cubic functions of the number of unknowns.

Table B1. Storage and Computation Comparison of Three Solution Algorithms.

|                       | Number of Unknowns | Number of Mult. and Divisions | Number of Storage Locations |
|-----------------------|--------------------|-------------------------------|-----------------------------|
| Modified Gauss Siedel | 100                | 400*                          | 900                         |
|                       | 500                | 2000*                         | 4500                        |
|                       | 1000               | 4000*                         | 9000                        |
| Gauss Siedel          | 100                | $1 \times 10^6$ *             | 10000                       |
|                       | 500                | $1.25 \times 10^8$ *          | $2.5 \times 10^5$           |
|                       | 1000               | $1.0 \times 10^9$ *           | $1.0 \times 10^6$           |
| Gaussian Elimination  | 100                | $2 \times 10^5$               | 10000                       |
|                       | 500                | $1.42 \times 10^6$            | $2.5 \times 10^5$           |
|                       | 1000               | $8.9 \times 10^7$             | $1.0 \times 10^6$           |

\* for the Gauss Siedel and the modified Gauss Siedel routines this represents the number of multiplications per convergence iteration.